



Synthesis, Characterization, and Applications of Oleic Acid Coated Kerosene-Based Fe_3O_4 Ferrofluids

¹Amit Nathani, ²Khushbu Patel, ³Ankit Shah, ⁴Shailesh Padsala and ⁵Manoj Godhaniya

¹Bhagwan Mahavir Centre for Advance Research, Bhagwan Mahavir University, Surat, Gujarat, India

²Department of Chemistry, Bhagwan Mahavir College of Basic & Applied Sciences, Bhagwan Mahavir University, Surat, Gujarat, India

³Department of Chemistry, SVNIT, Surat, Gujarat, India

⁴Shree Swami AtmanandSaraswatiVidhyaSankul, Surat, Gujarat, India

⁵Department of Biosciences, Veer Narmad South Gujarat University, Surat, Gujarat, India

Abstract: Ferrofluids are colloidal suspensions of magnetic nanoparticles in carrier liquids that exhibit unique magnetorheological properties. Kerosene-based ferrofluids containing oleic acid-coated magnetite (Fe_3O_4) nanoparticles have gained attention due to their excellent thermal stability, low volatility, and superior dispersion characteristics. This review examines the synthesis methodologies, characterization techniques, and diverse applications of oleic acid-coated kerosene-based Fe_3O_4 ferrofluids.

We analyzed chemical co-precipitation and thermal decomposition methods for Fe_3O_4 nanoparticle synthesis, emphasizing oleic acid's role as a surfactant in achieving stable colloidal dispersions. Characterization approaches discussed include X-ray diffraction (XRD) for phase identification, transmission electron microscopy (TEM) for morphological analysis, Fourier transform infrared spectroscopy (FTIR) for confirming oleic acid coating, vibrating sample magnetometry (VSM) for magnetic property evaluation, and rheological measurements for assessing flow behavior. The chemical bonding mechanisms between oleic acid and magnetite surfaces are critically analyzed.

The review highlights how oleic acid surface modification prevents particle agglomeration and enhances long-term stability in non-polar kerosene carriers. Characterization reveals distinct patterns in XRD peaks, magnetization curves, and viscosity-temperature relationships governing ferrofluid performance. Kerosene-based ferrofluids demonstrate superior performance in heat transfer enhancement for cooling systems, damping applications in shock absorbers and vibration control, and magnetic fluid sealing technology for rotary seals and vacuum feedthroughs. Emerging biomedical applications include drug delivery and magnetic hyperthermia therapy.

This review synthesizes current knowledge on oleic acid-coated kerosene-based Fe_3O_4 ferrofluids and identifies future research opportunities in nanoparticle size optimization, surface chemistry modification, and application-specific formulations, serving as a resource for researchers working on ferrofluid development across technological domains.

Index Terms - Ferrofluids, Magnetite nanoparticles, Oleic acid, Kerosene, Chemical co-precipitation

I. INTRODUCTION

Ferrofluids represent a unique class of smart materials that combine the fluid properties of liquids with the magnetic characteristics of solids, creating colloidal suspensions that respond to external magnetic fields while maintaining their fluidity [1]. These magnetically controllable fluids consist of nanoscale ferro or ferrimagnetic particles, typically 10-15 nm in diameter, dispersed in a carrier liquid with the aid

of surfactant molecules that prevent particle agglomeration through steric or electrostatic repulsion mechanisms [2].

Since their development by Papell in the 1960s for NASA's space program, ferrofluids have evolved into sophisticated functional materials with applications spanning thermal management, mechanical engineering, electronics, and biomedicine [3]. The selection of both the magnetic nanoparticle core and the carrier fluid significantly influences the performance characteristics and application domains of ferrofluids. Magnetite (Fe_3O_4) nanoparticles have emerged as the preferred magnetic component due to their high saturation magnetization, biocompatibility, chemical stability, and cost-effectiveness compared to other magnetic materials such as cobalt or nickel ferrites [4].

The carrier fluid selection is equally critical, with options including water, organic solvents, mineral oils, synthetic esters, and hydrocarbons. Among these, kerosene-based ferrofluids have gained prominence for industrial applications due to several advantageous properties: low volatility, good thermal stability across wide temperature ranges, excellent electrical insulation, chemical inertness, and commercial availability at reasonable cost [5]. Kerosene, a mixture of hydrocarbons primarily in the C10-C16 range, provides an ideal non-polar medium for applications requiring thermal management, electromagnetic shielding, and mechanical damping under varying environmental conditions.

Surface modification of magnetite nanoparticles is essential to achieve stable dispersion in non-polar kerosene carriers, as uncoated nanoparticles tend to aggregate due to van der Waals attractive forces and magnetic dipole-dipole interactions. Oleic acid (cis-9-octadecenoic acid, $\text{C}_{18}\text{H}_{34}\text{O}_2$) has become the surfactant of choice for kerosene-based ferrofluids due to its long hydrophobic alkyl chain, which provides excellent compatibility with non-polar solvents, and its carboxylic acid functional group, which forms strong chemical bonds with the hydroxyl groups on magnetite surfaces through chemisorption or complexation mechanisms [6], [7].

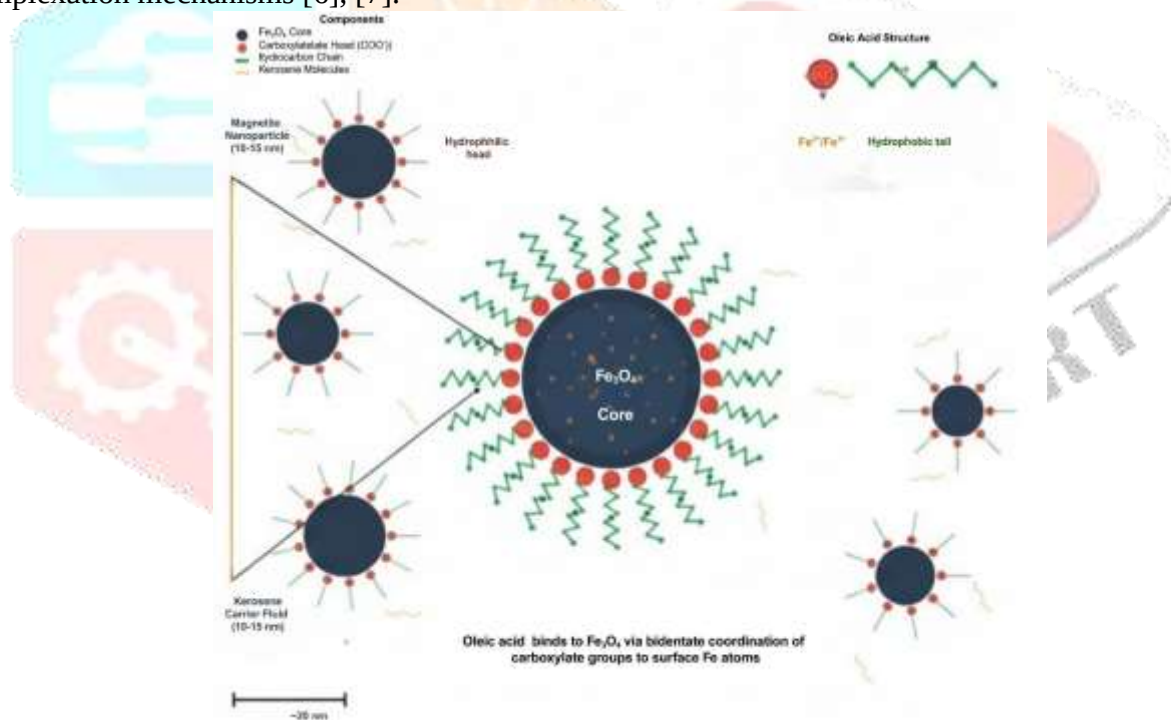


Figure 1. Structure of a ferrofluid showing Fe_3O_4 nanoparticles coated with oleic acid dispersed in a kerosene carrier

The stability of ferrofluids depends on surfactant-mediated interactions between Fe_3O_4 nanoparticles and carrier molecules (Figure 1). The oleic acid monolayer creates a steric barrier that prevents particle-particle contact while simultaneously rendering the nanoparticle surface hydrophobic and compatible with the kerosene medium. This surface engineering approach results in ferrofluids with enhanced colloidal stability, reduced sedimentation, improved magnetic responsiveness, and optimized rheological properties for specific applications [8], [9].

This review provides a comprehensive analysis of oleic acid-coated kerosene-based Fe_3O_4 ferrofluids, with emphasis on three critical aspects: (1) synthesis methodologies including chemical co-precipitation and thermal decomposition routes, with detailed examination of oleic acid coating mechanisms; (2) characterization techniques encompassing structural, morphological, chemical, magnetic, and rheological

analyses; and (3) applications with particular focus on heat transfer enhancement, damping systems, and magnetic sealing technology, while also addressing emerging biomedical uses.


II. SYNTHESIS AND SURFACE MODIFICATION TECHNIQUES

The synthesis of oleic acid-coated kerosene-based Fe₃O₄ ferrofluids involves two primary stages: (1) preparation of magnetite nanoparticles with controlled size, morphology, and crystallinity, and (2) surface modification with oleic acid to achieve stable dispersion in kerosene. This section examines the principal synthesis routes, surface chemistry, and factors governing ferrofluid stability.

Chemical Co-precipitation Method

Chemical co-precipitation is the most widely employed synthesis route for magnetite nanoparticles due to its simplicity, cost-effectiveness, ambient temperature operation, and ability to produce large quantities of nanoparticles with reasonable size control [10]. The method involves the simultaneous precipitation of Fe²⁺ and Fe³⁺ ions in an alkaline aqueous medium, typically using ammonia or sodium hydroxide as the precipitating agent.

The stoichiometric reaction for magnetite formation via co-precipitation can be represented as:



The synthesis typically begins with the preparation of aqueous solutions containing iron(II) chloride (FeCl₂) and iron(III) chloride (FeCl₃) in a molar ratio of 1:2. The mixed iron salt solution is then added dropwise to a vigorously stirred alkaline solution (pH > 9) maintained under an inert atmosphere (nitrogen or argon) to prevent oxidation of Fe²⁺ to Fe³⁺. The black precipitate of magnetite forms instantaneously and can be separated magnetically or through centrifugation [11].

Critical parameters affecting particle size, morphology, and magnetic properties include: (a) Fe²⁺/Fe³⁺ molar ratio - the theoretical 1:2 ratio yields pure magnetite phase, deviations lead to maghemite (γ-Fe₂O₃) or other iron oxide phases; (b) pH value - higher pH (>11) promotes smaller particles but may reduce crystallinity, while moderate pH (9-10) balances size and crystal quality; (c) temperature - elevated temperatures (60-90°C) enhance crystallinity and increase particle size through Ostwald ripening; (d) stirring rate - vigorous agitation promotes uniform nucleation and prevents local concentration gradients; (e) addition rate of reactants - slower addition rates allow controlled nucleation and narrow size distribution [12], [13].

Recent advances in co-precipitation methodology include the use of organic bases such as tetramethylammonium hydroxide, which produce smaller and more monodisperse particles, and continuous flow reactors that enable better process control and scalability [14]. Microwave-assisted co-precipitation has also been explored to achieve rapid heating, reduced reaction times, and enhanced crystallinity [15].

Thermal Decomposition Method

Thermal decomposition of iron precursors in high-boiling organic solvents represents an alternative synthesis route that typically yields magnetite nanoparticles with superior size monodispersity, crystallinity, and magnetic properties compared to co-precipitation. This method involves the pyrolysis of iron-containing organometallic compounds, such as iron pentacarbonyl [Fe(CO)₅], iron acetylacetonate [Fe(acac)₃], or iron oleate, in the presence of surfactants and high-boiling solvents like octadecene, benzyl ether, or trioctylamine.

The thermal decomposition process occurs through several stages: (1) decomposition of the iron precursor at elevated temperatures (typically 200-320°C), (2) nucleation of iron oxide nanocrystals, (3) growth of nuclei through diffusion of solubilized iron species, and (4) Ostwald ripening where smaller particles dissolve and larger particles grow [16]. The presence of surfactants such as oleic acid and oleylamine during synthesis serves multiple functions: capping agent to control particle size, stabilizer to prevent aggregation, and shape-directing agent to influence morphology.

A typical thermal decomposition synthesis involves mixing iron acetylacetonate with oleic acid, oleylamine, and a high-boiling solvent, followed by heating to reflux temperature (280-320°C) under inert atmosphere for 1-4 hours. The reaction mixture is then cooled, and nanoparticles are precipitated by adding ethanol or acetone, followed by magnetic separation [17]. The resulting nanoparticles are inherently coated with oleic acid, making them directly dispersible in non-polar solvents including kerosene.


Table 1. Comparison of chemical co-precipitation and thermal decomposition methods for Fe_3O_4 nanoparticle synthesis

Parameter	Chemical Co-precipitation	Thermal Decomposition
Reaction medium	Aqueous	Organic (high-boiling solvent)
Temperature (°C)	25–90	200–320
Particle size control	Moderate	Excellent
Crystallinity	Moderate	High
Cost & scalability	Low, scalable	High cost, limited scale
Surfactant requirement	Post-synthesis coating	In-situ coating possible

Both synthesis routes have specific advantages and limitations, as summarized in Table 1. Key advantages of thermal decomposition include: excellent size control through manipulation of reaction temperature, time, and precursor concentration; high crystallinity due to elevated synthesis temperatures; narrow size distribution (polydispersity index < 5%); and direct formation of oleic acid-coated nanoparticles eliminating post-synthesis surface modification [18]. However, this method requires more expensive precursors, high temperatures, and organic solvents, limiting its industrial scalability compared to aqueous co-precipitation.

Oleic Acid Surface Modification and Coating Mechanisms

The surface modification of magnetite nanoparticles with oleic acid is critical for achieving stable dispersion in non-polar kerosene carriers. Freshly synthesized magnetite nanoparticles possess hydrophilic surfaces rich in hydroxyl groups (-OH) and exhibit strong tendency toward agglomeration due to magnetic dipole-dipole interactions and van der Waals forces. Oleic acid, with its amphiphilic structure comprising a hydrophilic carboxylic acid head group (-COOH) and a long hydrophobic alkyl tail (C₁₇H₃₃-), serves as an ideal surfactant for rendering magnetite surfaces hydrophobic and compatible with non-polar solvents [6].

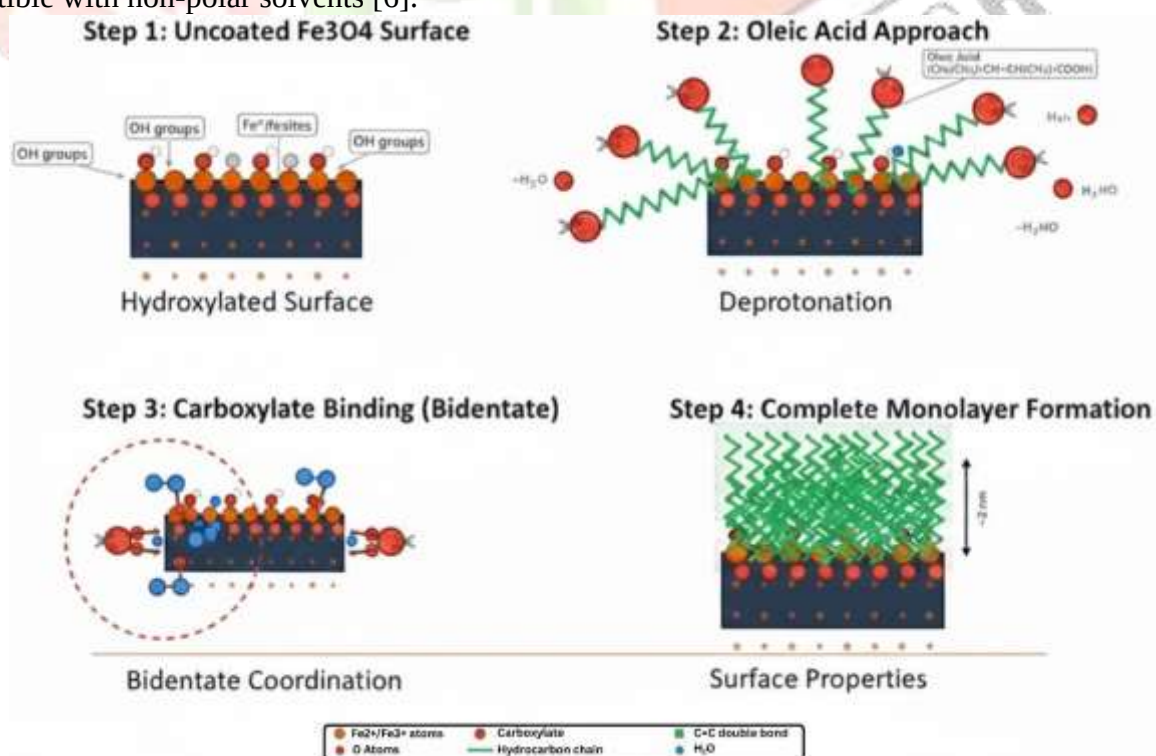**Figure 2.** Stepwise schematic representation of oleic acid coating on Fe_3O_4 nanoparticles showing carboxylate bonding to surface Fe^{2+}/Fe^{3+} sites and hydrophobic tail orientation

The coating process typically involves mixing magnetite nanoparticles (synthesized via co-precipitation or thermal decomposition) with excess oleic acid in an appropriate solvent, followed by heating (60–

80°C) with continuous stirring for several hours. The coating process involves chemisorption and bidentate coordination of carboxylate groups with Fe ions (Figure 2). During this process, oleic acid molecules adsorb onto the magnetite surface through various interaction mechanisms: (a) chemisorption - the carboxylic acid group forms covalent or coordinative bonds with surface $\text{Fe}^{2+}/\text{Fe}^{3+}$ cations; (b) hydrogen bonding - COOH groups interact with surface hydroxyl groups; (c) electrostatic attraction - ionized carboxylate groups ($-\text{COO}^-$) bind to positively charged surface sites [19].

Multiple studies have investigated the binding mode of oleic acid on magnetite surfaces using spectroscopic techniques. FTIR analysis reveals characteristic changes in the carboxylate stretching vibrations: the asymmetric COO^- stretch shifts from $\sim 1710\text{ cm}^{-1}$ (free oleic acid) to $\sim 1540\text{ cm}^{-1}$ (adsorbed oleate), while the symmetric stretch appears at $\sim 1440\text{ cm}^{-1}$, indicating bidentate coordination of carboxylate groups with surface iron atoms [20]. The separation between asymmetric and symmetric stretching frequencies ($\Delta\nu \approx 100\text{ cm}^{-1}$) suggests a bridging bidentate configuration where both oxygen atoms of the carboxylate group coordinate with surface Fe atoms.

The surface coverage and packing density of oleic acid molecules depend on several factors: (a) oleic acid concentration - excess oleic acid (typically 2-10 times the stoichiometric requirement) ensures complete monolayer coverage; (b) temperature - elevated temperatures enhance molecular mobility and facilitate reorganization of the surfactant layer; (c) pH - carboxylic acid groups dissociate at $\text{pH} > 5$, promoting binding to magnetite surfaces; (d) washing procedure - thorough washing with ethanol or acetone removes excess physisorbed oleic acid, leaving only chemisorbed monolayer [21]. Surface coverage is significantly affected by oleic acid concentration and temperature (Table 2).

Table 2. Summary of parameters influencing oleic acid coating efficiency on Fe_3O_4 nanoparticles.

Factor	Influence	Optimal Condition
Oleic acid concentration	Surface coverage	2–10× stoichiometric excess
Temperature	Molecular mobility	70–80 °C
pH	Carboxylic acid dissociation	> 5
Washing solvent	Removes unbound oleic acid	Ethanol or acetone
Particle size	Surface area	Smaller = higher coverage

Thermogravimetric analysis (TGA) provides quantitative assessment of surfactant loading on nanoparticle surfaces. For oleic acid-coated magnetite, weight loss between 200-500°C corresponds to decomposition and desorption of surface-bound oleic acid, typically ranging from 5-15 wt% depending on particle size and coating conditions. Smaller particles exhibit higher weight loss percentages due to larger surface area-to-volume ratios [22].

Ferrofluid Preparation in Kerosene Carrier

Following oleic acid surface modification, the hydrophobic magnetite nanoparticles can be dispersed in kerosene through simple mixing or sonication. The ferrofluid preparation process typically involves: (1) drying the oleic acid-coated nanoparticles to remove residual water and polar solvents; (2) adding a measured amount of dry nanoparticles to kerosene (typically 1-10 vol%); (3) ultrasonication for 30-60 minutes to break up soft agglomerates and achieve uniform dispersion; (4) magnetic decantation to remove any undispersed large particles or aggregates [23].

The stability of kerosene-based ferrofluids depends on the balance between attractive forces (magnetic dipole-dipole interactions, van der Waals forces) and repulsive forces (steric repulsion from oleic acid coating). The Stokes-Einstein equation governs Brownian motion of nanoparticles, preventing sedimentation despite the density difference between magnetite ($\sim 5.2\text{ g/cm}^3$) and kerosene ($\sim 0.8\text{ g/cm}^3$). Well-prepared ferrofluids should exhibit no visible sedimentation for months, magnetic responsiveness under applied fields, and smooth flow characteristics [15].

III. CHARACTERIZATION METHODS

Comprehensive characterization of oleic acid-coated kerosene-based Fe_3O_4 ferrofluids requires multiple analytical techniques to assess structural, morphological, chemical, magnetic, and rheological properties.

X-ray Diffraction (XRD) Analysis

X-ray diffraction serves as the primary technique for determining the crystal structure, phase purity, and crystallite size of magnetite nanoparticles. Magnetite (Fe_3O_4) exhibits an inverse spinel crystal structure with characteristic XRD peaks at 2θ values of approximately 30.1° , 35.5° , 43.1° , 53.4° , 57.0° , and 62.6° , corresponding to the (220), (311), (400), (422), (511), and (440) Miller indices [24].

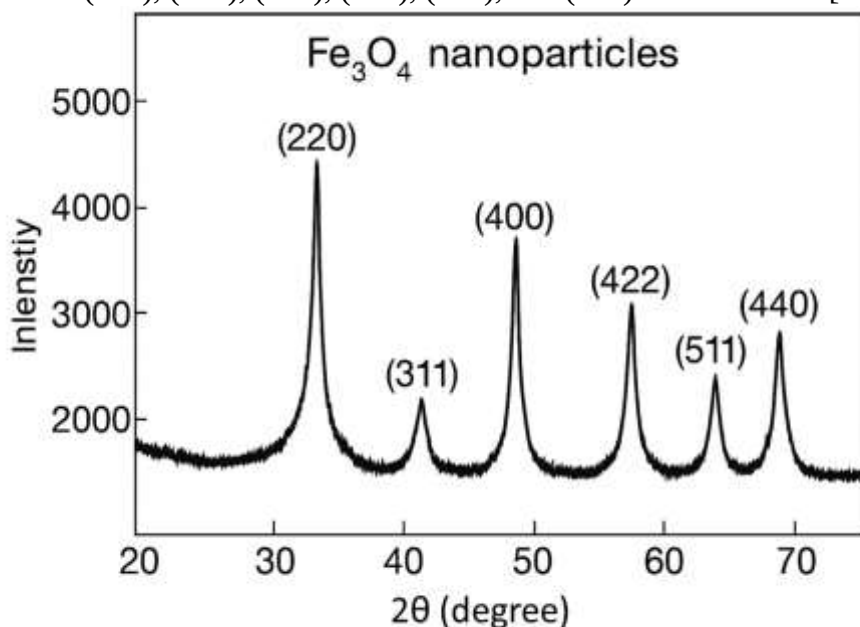


Figure 3. Representative XRD pattern of Fe_3O_4 nanoparticles showing diffraction peaks corresponding to (220), (311), (400), (422), (511), and (440) planes of the spinel structure.

The characteristic peaks at $2\theta \approx 30.1^\circ$, 35.5° , 43.1° , 53.4° , 57.0° , and 62.6° confirm the spinel Fe_3O_4 structure (Figure 3). The Scherrer equation enables estimation of average crystallite size from XRD peak broadening. For magnetite nanoparticles synthesized via chemical co-precipitation, typical crystallite sizes range from 8-25 nm depending on synthesis conditions [25].

Transmission Electron Microscopy (TEM)

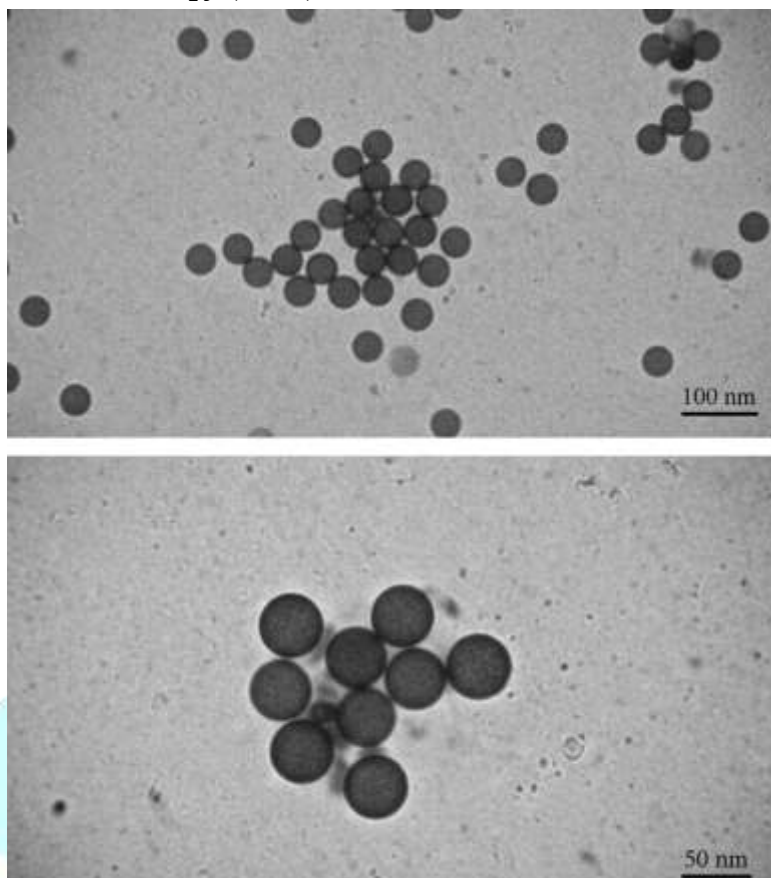


Figure 4. TEM images of oleic acid-coated Fe_3O_4 nanoparticles showing uniform spherical morphology and narrow size distribution.

TEM micrographs reveal quasi-spherical nanoparticles with average size of 10–20 nm (Figure 4). TEM provides direct visualization of nanoparticle morphology, size distribution, and core-shell structure. Well-synthesized nanoparticles typically exhibit quasi-spherical morphology with average diameters of 10–20 nm. High-resolution TEM reveals lattice fringes with the (311) plane spacing of 0.253 nm characteristic of magnetite [26].

Fourier Transform Infrared Spectroscopy (FTIR)

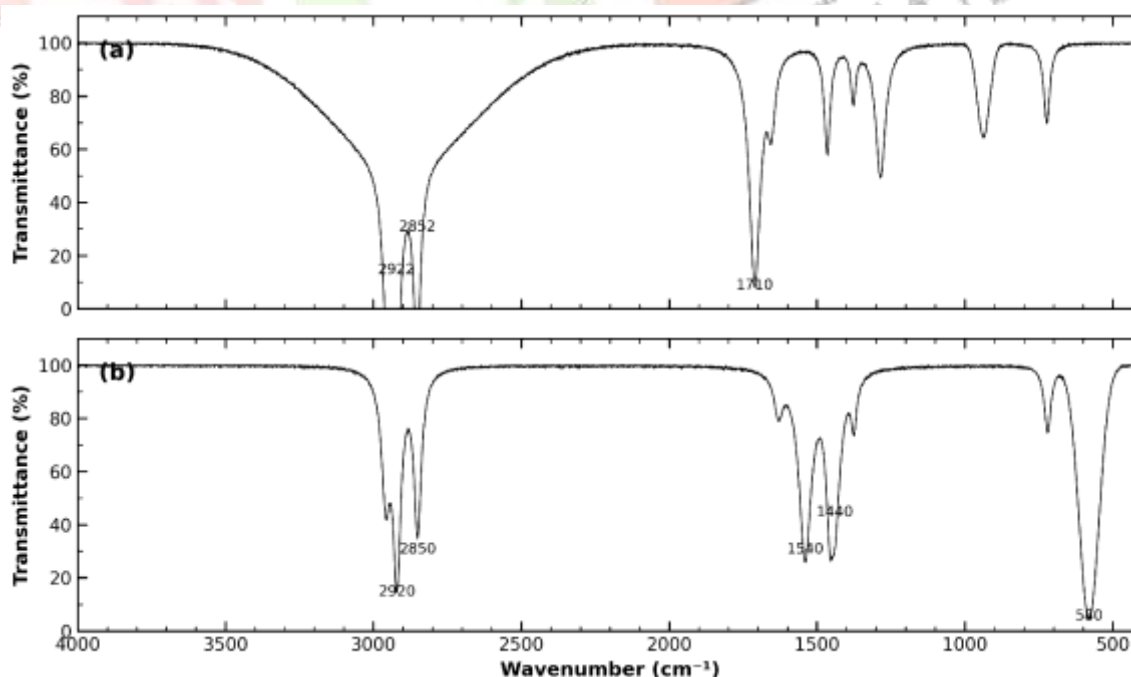


Figure 5. FTIR spectra of (a) pure oleic acid and (b) oleic acid-coated Fe_3O_4 nanoparticles, highlighting COO^- asymmetric ($\sim 1540\text{ cm}^{-1}$) and symmetric ($\sim 1440\text{ cm}^{-1}$) stretching vibrations.

FTIR spectroscopy provides crucial evidence for successful oleic acid coating. FTIR peaks at 1540 cm^{-1} and 1440 cm^{-1} confirm the formation of Fe–carboxylate bonds (Figure 5). The characteristic Fe–O stretching band appears around $570\text{--}630\text{ cm}^{-1}$. Upon oleic acid coating, C–H stretching vibrations appear

at ~ 2920 and ~ 2850 cm^{-1} , while asymmetric and symmetric COO^- stretches at ~ 1540 and ~ 1440 cm^{-1} indicate carboxylate coordination with surface Fe atoms [27].

Vibrating Sample Magnetometry (VSM)

VSM characterizes magnetic properties including saturation magnetization, remanence, and coercivity. For single-domain magnetite nanoparticles, superparamagnetic behavior is observed with zero coercivity and remanence at room temperature. Saturation magnetization typically ranges from 40-80 emu/g depending on particle size and oleic acid content [28].

Rheological Characterization

Rheological measurements assess flow behavior and viscosity. Kerosene-based ferrofluids exhibit Newtonian behavior at low concentrations with viscosity increasing under applied magnetic fields. Temperature dependence follows an Arrhenius relationship with viscosity decreasing exponentially at elevated temperatures [29].

IV. APPLICATIONS

Heat Transfer Enhancement

Ferrofluids demonstrate 20-40% thermal conductivity enhancement for 2-5 vol% magnetite in kerosene. Applications include electronic cooling, transformer cooling, automotive radiators, and heat exchangers. The superior thermal conductivity of magnetite nanoparticles compared to base fluids enables efficient heat dissipation [27].

Damping and Vibration Control

Magnetorheological properties enable adaptive damping where damping force varies with applied magnetic field. Applications include automotive suspension, seismic dampers, precision machinery isolation, and aerospace landing gear. Kerosene-based systems offer broader operating temperature ranges than water-based alternatives [15].

Magnetic Fluid Sealing

Ferrofluids held by magnetic field gradients create frictionless seals around rotating shafts. Applications include hard disk drives, vacuum feedthroughs, and chemical process equipment. Kerosene-based ferrofluids provide low vapor pressure, thermal stability, and chemical inertness essential for sealing applications [3].

Emerging Biomedical Applications

Oleic acid-coated magnetite nanoparticles in biocompatible carriers enable magnetic hyperthermia cancer therapy, targeted drug delivery, MRI contrast enhancement, and magnetic biosensing. These applications leverage superparamagnetic properties and biocompatibility of magnetite [30], [31]. The multifunctional nature of ferrofluids enables diverse industrial and biomedical applications (Table 3).

Table 3. Summary of key applications of oleic acid-coated kerosene-based Fe_3O_4 ferrofluids.

Application Area	Function	Key Property	References
Heat transfer systems	Cooling, heat exchangers	Enhanced thermal conductivity	[32]
Damping systems	Vibration absorption	Magnetorheological response	[33]
Magnetic sealing	Rotary vacuum seals	Low volatility, stability	[3]
Biomedical	Drug delivery, hyperthermia	Biocompatibility	[30]

Future Perspectives

Research opportunities include size optimization through advanced synthesis methods, exploration of alternative surfactants, development of multifunctional ferrofluids, comprehensive long-term stability studies, computational modeling for predictive design, sustainable green chemistry approaches, and establishment of standardized characterization protocols.

Conclusion

Oleic acid-coated kerosene-based Fe_3O_4 ferrofluids represent a mature yet evolving class of functional materials with diverse industrial applications. Chemical co-precipitation and thermal decomposition methods enable controlled nanoparticle synthesis, while oleic acid surface modification ensures stable dispersion in non-polar carriers. Comprehensive characterization through XRD, TEM, FTIR, VSM, and rheological measurements enables optimization for specific applications including heat transfer, damping, and sealing. Future research in synthesis optimization, surface chemistry modification, and application-specific formulations will expand ferrofluid technology impact across diverse technological domains.

V. ACKNOWLEDGMENT

The authors gratefully acknowledge the support of their respective institutions: BhagwanMahavir University, Surat; SardarVallabhbhai National Institute of Technology (SVNIT), Surat; Shree Swami AtmanandSaraswati Science College, Surat; and Veer Narmad South Gujarat University, Surat, for providing the academic and infrastructural environment that facilitated this work. The authors also thank the broader scientific community whose contributions to the field of ferrofluids and magnetic nanomaterials are cited in this review.

REFERENCES

- [1] S. Odenbach and S. Thurm, "Magnetoviscous Effects in Ferrofluids," in *Ferrofluids*, vol. 594, S. Odenbach, Ed., in Lecture Notes in Physics, vol. 594, Berlin, Heidelberg: Springer Berlin Heidelberg, 2002, pp. 185–201. doi: 10.1007/3-540-45646-5_10.
- [2] K. Raj and R. Moskowitz, "Commercial applications of ferrofluids," *Journal of Magnetism and Magnetic Materials*, vol. 85, no. 1–3, pp. 233–245, Apr. 1990, doi: 10.1016/0304-8853(90)90058-X.
- [3] R. E. Rosensweig, "Continuum equations for magnetic and dielectric fluids with internal rotations," *The Journal of Chemical Physics*, vol. 121, no. 3, pp. 1228–1242, July 2004, doi: 10.1063/1.1755660.
- [4] S. Laurent *et al.*, "Magnetic Iron Oxide Nanoparticles: Synthesis, Stabilization, Vectorization, Physicochemical Characterizations, and Biological Applications," *Chem. Rev.*, vol. 108, no. 6, pp. 2064–2110, June 2008, doi: 10.1021/cr068445e.
- [5] R. González-Martín, A. Gutiérrez-Serpa, and V. Pino, "The Use of Ferrofluids in Analytical Sample Preparation: A Review," *Separations*, vol. 8, no. 4, p. 47, Apr. 2021, doi: 10.3390/separations8040047.
- [6] B. Panda and P. S. Goyal, "Oleic acid coated magnetic nano-particles: Synthesis and characterizations," presented at the NANOFORUM 2014, Rome, Italy, 2015, p. 050020. doi: 10.1063/1.4917661.
- [7] T. Marín, P. Montoya, O. Arnache, and J. Calderón, "Influence of Surface Treatment on Magnetic Properties of Fe_3O_4 Nanoparticles Synthesized by Electrochemical Method," *J. Phys. Chem. B*, vol. 120, no. 27, pp. 6634–6645, July 2016, doi: 10.1021/acs.jpcc.6b01796.
- [8] N. Joumaa, P. Toussay, M. Lansalot, and A. Elaissari, "Surface modification of iron oxide nanoparticles by a phosphate-based macromonomer and further encapsulation into submicrometer polystyrene particles by miniemulsion polymerization," *J. Polym. Sci. A Polym. Chem.*, vol. 46, no. 1, pp. 327–340, Jan. 2008, doi: 10.1002/pola.22383.
- [9] V. I. Petrenko *et al.*, "Magnetic Fluids: Structural Aspects by Scattering Techniques," in *Modern Problems of Molecular Physics*, vol. 197, L. A. Bulavin and A. V. Chalyi, Eds., in Springer Proceedings in Physics, vol. 197, Cham: Springer International Publishing, 2018, pp. 205–226. doi: 10.1007/978-3-319-61109-9_10.
- [10] R. Massart, "Preparation of aqueous magnetic liquids in alkaline and acidic media," *IEEE Trans. Magn.*, vol. 17, no. 2, pp. 1247–1248, Mar. 1981, doi: 10.1109/TMAG.1981.1061188.
- [11] Helendra, N. I. Istiqomah, H. Sabarman, and E. Suharyadi, "Synthesis of varied oleic acid-coated Fe_3O_4 nanoparticles using the co-precipitation technique for biosensor applications," *Sensors International*, vol. 6, p. 100295, 2025, doi: 10.1016/j.sintl.2024.100295.
- [12] O. Karaagac and H. Kockar, "Effect of Synthesis Parameters on the Properties of Superparamagnetic Iron Oxide Nanoparticles," *J Supercond Nov Magn*, vol. 25, no. 8, pp. 2777–2781, Dec. 2012, doi: 10.1007/s10948-011-1264-8.

- [13] M. Mahmoudi, A. Simchi, M. Imani, A. S. Milani, and P. Stroeve, "Optimal Design and Characterization of Superparamagnetic Iron Oxide Nanoparticles Coated with Polyvinyl Alcohol for Targeted Delivery and Imaging," *J. Phys. Chem. B*, vol. 112, no. 46, pp. 14470–14481, Nov. 2008, doi: 10.1021/jp803016n.
- [14] B. Unal, Z. Durmus, H. Kavas, A. Baykal, and M. S. Toprak, "Synthesis, conductivity and dielectric characterization of salicylic acid-Fe₃O₄ nanocomposite," *Materials Chemistry and Physics*, vol. 123, no. 1, pp. 184–190, Sept. 2010, doi: 10.1016/j.matchemphys.2010.03.080.
- [15] S. V. Ganachari, N. R. Banapurmath, J. S. Yaradoddi, V. B. Patil, A. Yavagal, and P. Mogre, "Synthesis and characterisation of iron oxide (Fe₃O₄) ferrofluid nanoparticles coated by poly (vinyl butyral) with microsphere," *MNS*, vol. 13, Mar. 2021, doi: 10.2174/1876402913666210308142702.
- [16] T. Hyeon, S. S. Lee, J. Park, Y. Chung, and H. B. Na, "Synthesis of Highly Crystalline and Monodisperse Maghemite Nanocrystallites without a Size-Selection Process," *J. Am. Chem. Soc.*, vol. 123, no. 51, pp. 12798–12801, Dec. 2001, doi: 10.1021/ja016812s.
- [17] M. Nahorniak *et al.*, "Two-step single-reactor synthesis of oleic acid- or undecylenic acid-stabilized magnetic nanoparticles by thermal decomposition method," Mar. 02, 2022, *nanotechnology*. doi: 10.3762/bxiv.2022.12.v1.
- [18] M. Nasrollahzadeh, "Advances in Magnetic Nanoparticles-Supported Palladium Complexes for Coupling Reactions," *Molecules*, vol. 23, no. 10, p. 2532, Oct. 2018, doi: 10.3390/molecules23102532.
- [19] H.-C. Roth, S. Schwaminger, P. Fraga García, J. Ritscher, and S. Berensmeier, "Oleate coating of iron oxide nanoparticles in aqueous systems: the role of temperature and surfactant concentration," *J Nanopart Res*, vol. 18, no. 4, p. 99, Apr. 2016, doi: 10.1007/s11051-016-3405-2.
- [20] J. Moradiganjeh and Z. Aghajani, "Synthesis and characterization of novel magnetic Fe₃O₄/C through the Co-precipitation method and investigation of its desulfurization application," *J Mater Sci: Mater Electron*, vol. 27, no. 6, pp. 5948–5953, June 2016, doi: 10.1007/s10854-016-4515-4.
- [21] R. Moarref and S. Pourmahdian, "Preparation of Fe₃O₄/Polymethyl Methacrylate Composite Particles from Monolayer Oleic Acid-Modified Fe₃O₄," in *Eco-friendly and Smart Polymer Systems*, H. Mirzadeh and A. A. Katbab, Eds., Cham: Springer International Publishing, 2020, pp. 371–374. doi: 10.1007/978-3-030-45085-4_89.
- [22] A. G. Roca *et al.*, "Magnetite nanoparticles with no surface spin canting," *Journal of Applied Physics*, vol. 105, no. 11, p. 114309, June 2009, doi: 10.1063/1.3133228.
- [23] V. Mikelashvili *et al.*, "Synthesis and Characterization of Citric Acid-Modified Iron Oxide Nanoparticles Prepared with Electrohydraulic Discharge Treatment," *Materials*, vol. 16, no. 2, p. 746, Jan. 2023, doi: 10.3390/ma16020746.
- [24] S. Baghshahi and F. Yousefi, "A New Systematic Approach to the Morphology and Magnetic Properties of Spherical, Cubic, and Rod-like Magnetite Nanoparticles," *J Supercond Nov Magn*, vol. 34, no. 7, pp. 1949–1954, July 2021, doi: 10.1007/s10948-021-05884-0.
- [25] H. Kızıltas, T. TekiN, D. BiRhan, and D. TekiN, "Synthesis and characterization of magnetically separable Fe₃O₄@SiO₂@TiO₂-Ag composite for degradation of Acid Blue 161," Dec. 05, 2024, *In Review*. doi: 10.21203/rs.3.rs-4977985/v1.
- [26] M. Wang and M. Deng, "Synthesis and characterization of fluorescent magnetic Fe₃O₄/CdTe@SiO₂-NH-FA nanoprobe," *Materials Letters*, vol. 309, p. 131358, Feb. 2022, doi: 10.1016/j.matlet.2021.131358.
- [27] C. Moya, X. Batlle, and A. Labarta, "The effect of oleic acid on the synthesis of Fe_{3-x} O₄ nanoparticles over a wide size range," *Phys. Chem. Chem. Phys.*, vol. 17, no. 41, pp. 27373–27379, 2015, doi: 10.1039/C5CP03395K.
- [28] M. Ognjanović, M. Bošković, H. Kolev, B. Dojčinović, S. Vranješ-Đurić, and B. Antić, "Synthesis, Surface Modification and Magnetic Properties Analysis of Heat-Generating Cobalt-Substituted Magnetite Nanoparticles," *Nanomaterials*, vol. 14, no. 9, p. 782, Apr. 2024, doi: 10.3390/nano14090782.
- [29] A. A. Ibiyemi, G. T. Yusuf, and A. Olusola, "Influence of temperature and magnetic field on rheological behavior of ultra-sonicated and oleic acid coated cobalt ferrite ferrofluid," *Phys. Scr.*, vol. 96, no. 12, p. 125842, Dec. 2021, doi: 10.1088/1402-4896/ac2ecb.
- [30] P. B. Shete, R. M. Patil, B. M. Tiwale, and S. H. Pawar, "Water dispersible oleic acid-coated Fe₃O₄ nanoparticles for biomedical applications," *Journal of Magnetism and Magnetic Materials*, vol. 377, pp. 406–410, Mar. 2015, doi: 10.1016/j.jmmm.2014.10.137.

- [31] A. El-Kholany and D. T. Gebreel, "Physical Studies and Hyperthermia Biomedical Modeling Application of Fe₃O₄ Magnetic Nanoclusters Coated with Barbituric Acid," May 30, 2024, *In Review*. doi: 10.21203/rs.3.rs-4364432/v1.
- [32] M. Imran *et al.*, "Ferrofluid synthesis using oleic acid coated Fe₃O₄ nanoparticles dispersed in mineral oil for heat transfer applications," *Mater. Res. Express*, vol. 5, no. 3, p. 036108, Mar. 2018, doi: 10.1088/2053-1591/aab4d7.
- [33] M. Victory, R. P. Pant, and S. Phanjoubam, "Synthesis and characterization of oleic acid coated Fe–Mn ferrite based ferrofluid," *Materials Chemistry and Physics*, vol. 240, p. 122210, Jan. 2020, doi: 10.1016/j.matchemphys.2019.122210.

